

HYDROTHERMAL GROWTH AND SQUEEGEE METHOD IN THE FABRICATION OF MIXED-PHASE TiO₂ NANOSTRUCTURES

Muqoyyanah^{1,2}, Suriani Abu Bakar^{1,2*}, Azmi Mohamed^{1,3}, Norhayati Hashim^{1,3},
Mohamad Hafiz Mamat⁴, Mohd Firdaus Malek^{4,5}, and Mohd Khairul Ahmad⁶
*e-mail: absuriani@yahoo.com

¹Nanotechnology Research Centre,

²Department of Physics,

³Department of Chemistry,

Faculty of Science and Mathematics, Universiti Pendidikan Sultan Idris,
35900 Tanjung Malim, Perak, Malaysia.

⁴NANO-ElecTronic Centre (NET), Faculty of Electrical Engineering,

⁵NANO-SciTech Centre (NST), Institute of Science (IOS),

Universiti Teknologi MARA (UiTM), 40450 Shah Alam, Selangor, Malaysia.

⁶Microelectronic and Nanotechnology–Shamsuddin Research Centre (MiNT-SRC),
Faculty of Electrical and Electronic Engineering, Universiti Tun Hussein Onn
Malaysia, 86400 Parit Raja, Batu Pahat, Johor, Malaysia.

ABSTRACT

In this work, the modification of TiO₂ nanostructures based on its morphology and crystallinity phase were fabricated using a simple method. Hydrothermal growth method was used to synthesize nanorods and nanoflowers, while nanoparticles was applied using squeegee method. The average length and diameter of the as-grown nanorods were 3.5 and 46-215 nm, respectively. Meanwhile, the average total thickness and band gap value of mixed-phase TiO₂ nanostructures were 15.98-24.54 nm and 2.84 eV, respectively. Based on its structural and electrical properties, the fabricated film has great potential to be applied as photoanode semiconductor layer for dye-sensitized solar cells application.

Key words: TiO₂, Nanostructures, Mixed-phase, Hydrothermal, Squeegee.

ABSTRAK

Dalam penelitian ini, modifikasi struktur nano TiO₂ berdasarkan morfologi dan fase kristalinitasnya difabrikasi menggunakan metode sederhana. Metode pertumbuhan hidrotermal digunakan untuk mensintesis batang nano dan bunga nano, sementara untuk partikel nano diterapkan menggunakan metode squeegee. Rata-rata panjang dan diameter batang nano adalah masing-masing 3,5 dan 46-215 nm. Sementara itu, total rata-rata ketebalan dan nilai *band gap* dari fase campuran struktur nano TiO₂ adalah masing-masing 15,98-24,54 nm dan 2,84 eV. Berdasarkan sifat struktural dan listriknya, film yang dibuat memiliki potensi besar untuk diaplikasikan sebagai lapisan semikonduktor fotoanoda untuk aplikasi sel surya *dye-sensitized*.

Kata kunci: TiO₂, struktur nano, fase campuran, hidrotermal, Squeegee.

INTRODUCTION

Titanium dioxide (TiO_2) becomes the most investigated metal oxides materials due to its wide range of applications and suitable for many experimental techniques (Diebold, 2003). TiO_2 has several nanostructures, such as nanoparticle, nanorod, nanoflower, nanowire, nanotube, and hollow hemisphere. Meanwhile, anatase, rutile, and brookite are the crystallinity phase known for TiO_2 . Each nanostructures and crystallinity phase have its own advantages and disadvantages. Brookite is known as metastable phase thus rarely used, while rutile is known as the most stable phase among other phases and has larger grain size as compared to anatase. The smaller grain size of anatase becomes an advantage due to the larger surface area as compared to rutile. Anatase also has the widest band gap (E_g) among other phases which is useful in electronic applications [Lei, *et.al.*, 2016]. Based on those facts, the synthesis of mixed-phase TiO_2 between rutile and anatase could yield a better electrical performance (Mehmood, *et.al.*, 2014). Some methods to synthesize TiO_2 are pulsed laser deposition, hydrolysis method, hydrothermal growth, and solvothermal method.

Photocatalyst material, gas sensor, corrosion-protective coating, optical coating, Li-based batteries, and electrochromic devices are some of the applications which utilize TiO_2 . In addition, TiO_2 is also used in paint industries and cosmetic products as white pigment and even in medical as bone implant (Diebold, 2003). Among those applications, TiO_2 as photocatalyst material gains a lot of interest since the invention of dye-

sensitized solar cells (DSSCs) in 1991 (O'Regan and Grätzel, 1991; Ahmad, *et.al.*, 2015; Zhang, *et.al.*, 2006; Lee, *et.al.*, 2014). Based on several investigations, TiO_2 shows better performance as compared to ZnO and SnO_2 which are usually used as photoanode semiconductor layer (Han, *et.al.*, 2009; Fukai, *et.al.*, 2007; Bauer, *et.al.*, 2002). Moreover, the properties of TiO_2 which are chemically and physically stable, low-cost, good electronic properties, non-toxic, and large effective surface area are needed in dye adsorption process and suitable as well as become the advantages for DSSCs application (Lei, *et.al.*, 2016, Qin, *et.al.*, 2015; Tamilselvan, *et.al.*, 2012; Hwang, *et.al.*, 2012). The adsorption process becomes an important factor in DSSCs process which affect the DSSCs energy conversion efficiency (η). The η value is affected by the amount of flowing electrons through the circuit indicated by short current density (J_{sc}) value. The morphology and crystallinity phase of TiO_2 absolutely affect the J_{sc} value thus their crystallinity need to be greatly considered in terms of structural optimization (Mehmood, *et.al.*, 2014; Zhu, *et.al.*, 2014; Gong, *et.al.*, 2012). Another important factor is the chosen substrate which should have high electrical conductivity and optically transparent. Sima *et al.* (Sima, *et.al.*, 2010) investigated the DSSCs performance by comparing indium-doped tin oxide and fluorine-doped tin oxide (FTO) as substrates. Based on the result, FTO shows a lower sheet resistance and thermally-stable thus it is recommended for DSSCs application.

In this work, we synthesize rutile TiO₂ nanorods—nanoflowers and mix them with anatase TiO₂ nanoparticles. Nanorods and nanoflowers were synthesized using hydrothermal growth (Ahmad, *et.al.*, 2015), while nanoparticles was synthesized using squeegee method (Zhang, *et.al.*, 2006).

MATERIALS AND METHODS

FTO substrate was cut into 2×1 cm² dimension and cleaned using acetone, methanol, and deionize (DI) water for 15 minutes, respectively. The substrate was then placed on autoclave with the conductive surface facing upward. Hydrothermal solution for TiO₂ nanorods and nanoflowers growth were prepared based on previous study conducted by Ahmad, et al. [Ahmad, *et.al.*, 2015]. 120 ml of hydrochloric acid and 120 ml of DI water was stirred for 5 minutes until well-mixed before adding 6 ml of titanium butoxide dispersing drop by drop to the solution. Clear hydrothermal solution was obtained after stirring for another 10 minutes and directly poured into autoclave. Hydrothermal growth process was performed at 150°C for 5 hours. The grown films were then taken out from the autoclave after cooled down to room temperature followed by rinsing using DI water and drying in room temperature.

The second layer of the film was produced by applying TiO₂ paste based on simple squeegee method (Zhang, *et.al.*, 2006) on top of the as-grown TiO₂ nanorods and nanoflowers. 7.5 ml of ethanol was poured into 1.75 g titanium (IV) oxide and stirred until a paste formed followed by adding 0.25 ml of titanium (IV) isopropoxide and stirred until the prepared paste became

well-mixed with low agglomeration. The obtained paste was sonicated for 5 minutes in room temperature and rolled over the fabricated film's first layer using glass rod and heated in electric oven for 10 minutes at 150°C. The films was annealed at 450°C for 1 hour before processing with physical characterizations. Several characterization, such as field emission scanning electron microscopy (FESEM), micro-Raman spectroscopy, energy dispersive X-ray (EDX), and UV-Vis spectroscopy were used to investigate the morphology, lattice crystallinity, and electrical performance of the fabricated film.

RESULTS AND DISCUSSIONS

FESEM images of the as-grown TiO₂ nanorods are presented in Fig. 1. Based on Fig. 1 (a), it can be shown that the synthesized nanorods was grown uniformly and densely. The crystal structure of nanorods was in tetragonal shape with diameters range of 46–215 nm as shown in Fig. 1 (b). Cross section image of fabricated film's first layer in Fig. 1 (c) reveals the perpendicular direction and high-density nanorods grown on FTO substrate. The results was in good agreement with Ahmad et al. (Ahmad, *et.al.*, 2015). Several size of nanoflowers which grow rarely in some spot of nanorods were also observed. The average length of nanorods was 3.5 nm, which was a bit longer compared to the previous result (Ahmad, *et.al.*, 2015). Anatase TiO₂ nanoparticles was also seen to be uniformly spread and completely covered nanorods as shown in Fig. 1 (d). The large surface area of nanoparticles due to the small grain size of particles gives an advantage if it

is applied as photoanode semiconductor layer which increase the dye adsorption. The study reveal that the maximum dye adsorption led to the increment of electron excitation thus improve the J_{SC} value. As a result of this, high η will be achieved. A closer view in Fig. 1 (e) shows a closely interconnected particles which is believed to give an advantage in electrons transfer to the nanorods. The shape and direction of as-grown

nanorods perpendicular to the substrate makes the electrons directly and easily move to FTO substrate. Fig. 1 (f) shows the cross section view of fabricated film thickness. Based on the image, the film thickness range from 15.98 to 24.54 μm . EDX analysis as shown in Table 1 confirms titanium and oxygen as element compound of fabricated mixed-phase TiO_2 nanostructures.

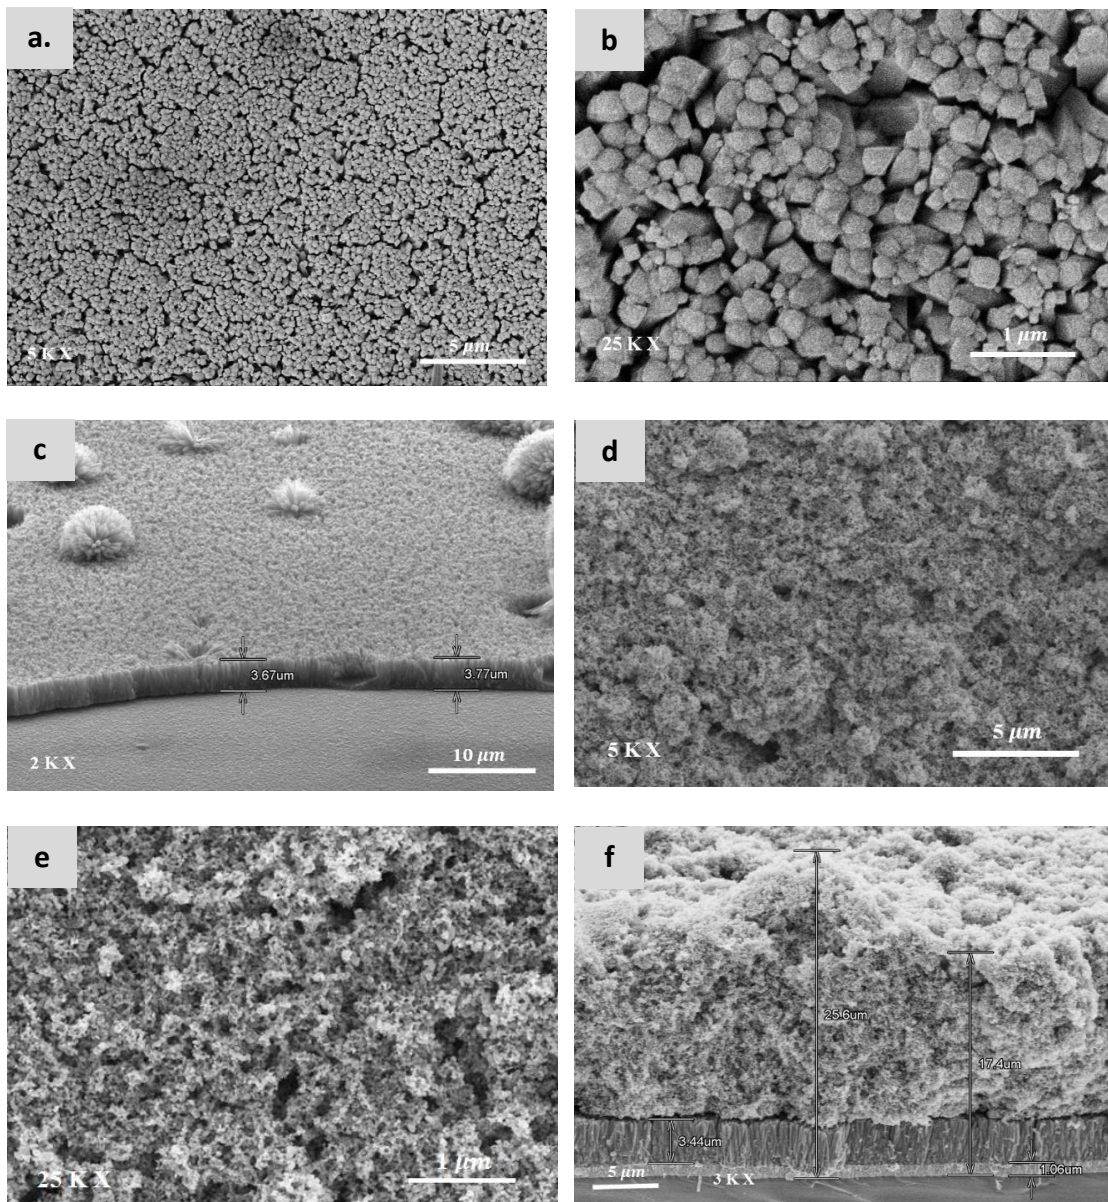


Fig. 1. FESEM images of fabricated mixed-phase TiO₂ nanostructures; (a)-(b) TiO₂ nanorods top view and (c) its cross section which contains nanoflowers, (d)-(e) TiO₂ nanoparticles top view and (f) fabricated film thickness cross section.

Table 1. EDX analysis of fabricated mixed-phase TiO₂ nanostructures.

| Element compound | Weight (%) | Atomic (%) |
|------------------|------------|------------|
| Titanium (Ti) | 56.05 | 29.87 |
| Oxygen (O) | 43.95 | 70.13 |

Fig. 2 shows micro-Raman spectra for both nanorods and mixed-phase of TiO₂ nanostructures films. Based on Fig. 2 (a), the synthesized TiO₂ nanorods was confirmed in rutile phase shown by four major peaks at 117, 237, 444, and 607 cm⁻¹. Two prominent peaks at 444 and 607 cm⁻¹ shows a high intensity indicated that there were lots of nanorods compared to nanoflowers which confirm the analysis by FESEM. The micro-Raman spectra of mixed-phase TiO₂ did not shifted much after nanoparticles were

applied on top of the nanorods as shown in Fig. 2 (b). The additional peaks at 144 and 516 cm⁻¹ are known as anatase phase which confirmed that the synthesized film are in mixed-phase of rutile and anatase phase. The two prominent peaks of rutile phase in Fig. 2 (b) also slightly shifted to higher wavelength and its intensity also decreases which might be caused by nanoparticles that covers the nanorods (Balachandran and Eror, 1982; Aprile, *et.al.*, 2008; Luo, *et.al.*, 2014; Ahmad, *et.al.*, 2016).

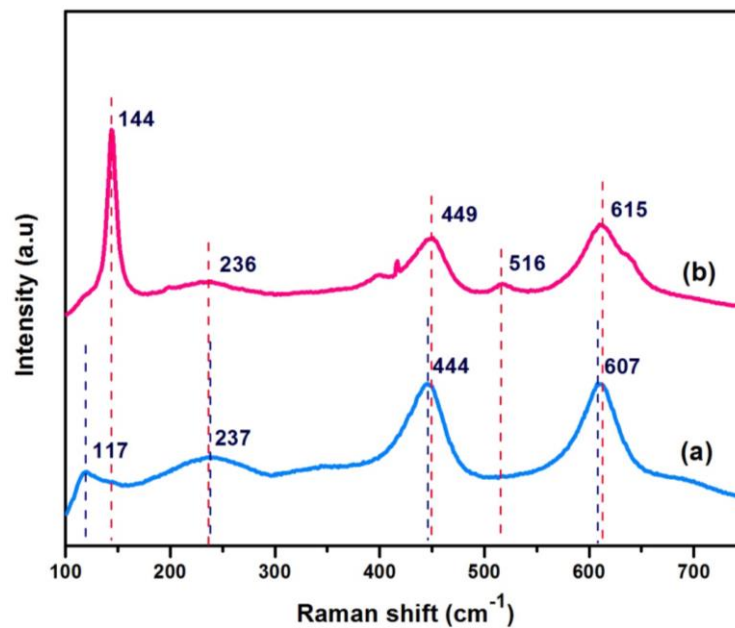


Fig. 2. Micro-Raman spectra of; (a) TiO₂ nanorods and (b) mixed-phase TiO₂ nanostructures.

The E_g value of fabricated TiO₂ nanostructures were calculated from UV-Vis data. The plotted graph shown

in Fig. 3 shows the large difference of E_g value between rutile TiO₂ nanorods and mixed-phase TiO₂ nanostructures.

The calculated E_g for rutile TiO_2 nanorods is 3.06 eV while the mixed-phase TiO_2 is 2.84 eV which is in the range of TiO_2 band gap. The obtained

E_g value of pure rutile is similar with previous report (Lei, *et.al.*, 2016).

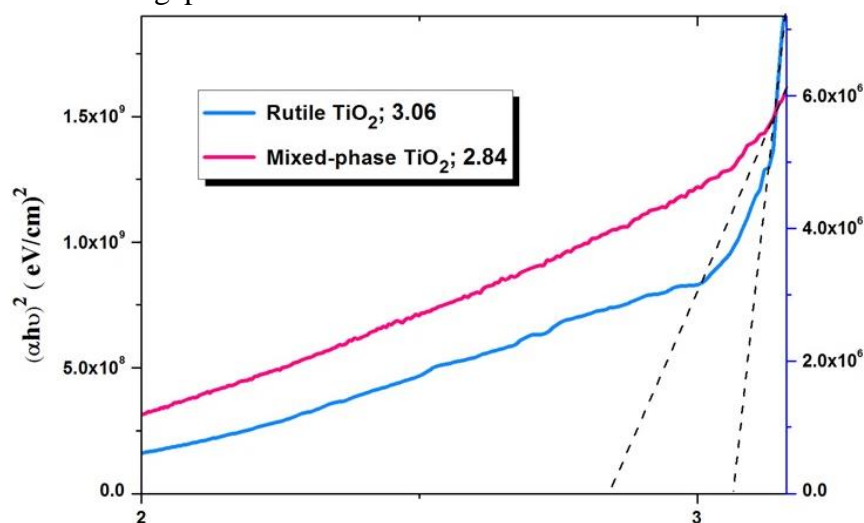


Fig. 3. Band gap value of TiO_2 nanorods and mixed-phase TiO_2 nanostructures.

CONCLUSION

In this study, we successfully synthesized mixed-phase TiO_2 nanostructures which contains bilayer TiO_2 nanorods-nanoflowers and nanoparticles. The rutile nanorods-nanoflowers and anatase nanoparticles were synthesized using hydrothermal growth and squeegee method, respectively. The average length of as-grown nanorods were 3.5 nm with the diameter range of 46-215 nm. Meanwhile, the average total thickness and band gap value of mixed-phase TiO_2 nanostructures were 15.98-24.54 nm and 2.84 eV, respectively. This value is acceptable and the synthesized film has great potential to be applied as photoanode semiconductor layer for DSSCs application.

ACKNOWLEDGEMENT

The authors would like to express their appreciation to the TWAS-COMSTECH Research Grants (2017-0001-102-11), National Nanotechnology Directorate Division (2014-0015-102-03) and Fundamental Research Grant Scheme (2015-0154-102-02) for financial support on this project.

REFERENCES

- Ahmad, M. K., S. M. Mokhtar, C. F. Soon, N. Nafarizal, A. B. Suriani, A. Mohamed, M. H. Mamat, M. F. Malek, M. Shimomura, and K. Murakami. 2016. *Raman Investigation of Rutile-phased TiO_2 Nanorods/Nanoflowers with Various Reaction Times Using One Step Hydrothermal Method*. J. Mater. Sci.: Mater Electron. doi 10.1007/s10854-016-4783-z.

- Ahmad, M. K., V. M. Mohan, and K. Murakami. 2015. *Hydrothermal Growth of Bilayered Rutile-phased TiO₂ Nanorods/Micro-size TiO₂ Flower in Highly Acidic Solution for Dye-sensitized Solar Cell*. J. Sol-Gel Sci. and Technol.73:655-659.
- Aprile, C., L. Maretti, M. Alvaro, J. C. Scaiano, and H. Garcia. 2008. *Long-Lived (Minutes) Photoinduced Charge Separation in A Structured Periodic Mesoporous Titania Containing 2,4,6-triphenylpyrylium as Guest*. Dalton Transactions.5465-5470.
- Balachandran, U. and N. G. Eror. 1982. *Raman Spectra of Titanium Dioxide*. Journal of Solid State Chemistry.42:276-282.
- Bauer, C., G. Boschloo, E. Mukhtar, and A. Hagfeldt. 2002. *Ultrafast Studies of Electron Injection in Ru Dye Sensitized SnO₂ Nanocrystalline Thin Film*. International Journal of Photoenergy.4(1):17-20.
- Diebold, U. 2003. *The Surface Science of Titanium Dioxide*. Surface Science Reports.48:53-229.
- Fukai, Y., Y. Kondo, S. Mori, and E. Suzuki. 2007. *Highly Efficient Dye-sensitized SnO₂ Solar Cells Having Sufficient Electron Diffusion Length*. Electrochemistry Communications.9(7):1439-1443.
- Gong, J., J. Liang, and K. Sumathy. 2012. *Review on Dye-sensitized Solar Cells (DSSCs): Fundamental Concepts and Novel Materials*. Renewable and Sustainable Energy Reviews.16:5848-5860.
- Han, D.-W., J.-H. Heo, D.-J. Kwak, C.-H. Han, and Y.-M. Sung. 2009. *Texture, Morphology and Photovoltaic Characteristics of Nanoporous F:SnO₂ Films*. Journal of Electrical Engineering and Technology.4(1):93-97.
- Hwang, Y. J., C. Hahn, B. Liu, and P. Yang. 2012. *Photoelectrochemical Properties of TiO₂ Nanowire Arrays: A Study of the Dependence on Length and Atomic Layer Deposition Coating*. American Chemical Society.6(6):5060-5069.
- Lee, K.-M., L.-C. Lin, V. Suryanarayanan, and C.-G. Wu. 2014. *Titanium Dioxide Coated on Titanium/Stainless Steel Foil as Photoanode for High Efficiency Flexible Dye-sensitized Solar Cells*. Journal of Power Sources.269:789-794.
- Lei, J., H. Li, J. Zhang, and M. Anpo. 2016. *Mixed-Phase TiO₂ Nanomaterials as Efficient Photocatalysts*. Springer. 423-429.
- Luo, Z., A. S. Poyraz, C.-H. Kuo, R. Miao, Y. Meng, S.-Y. Chen, T. Jiang, C. Wenos, and S. L. Suib. 2014. *Crystalline Mixed Phase (Anatase/Rutile) Mesoporous Titanium Dioxides for Visible Light Photocatalytic Activity*. Chemistry of Materials. dx.doi.org/10.1021/cm5035112.
- Mehmood, U., A. Rahman, K. Harrabi, I. A. Hussein, and B. V. S. Reddy. 2014. *Recent Advances in Dye Sensitized Solar Cells*. Advances in Materials Science and Engineering. <http://dx.doi.org/10.1155/2014/97478>
- O'Regan, B. and M. Grätzel. 1991. *A Low-cost, High-efficiency Solar Cell Based on Dye-Sensitized Colloidal TiO₂ Films*. Nature. 353:737-740.
- Qin, D.-D., Y.-P. Bi, X.-J. Feng, W. Wang, G. D. Barber, T. Wang, Y.-M. Song, X.-Q. Lu, and T. E. Mallouk. 2015. *Hydrothermal Growth and*

- Photoelectrochemistry of Highly Oriented, Crystalline Anatase TiO₂ Nanorods on Transparent Conducting Electrodes.* Chemistry of Materials.27:4180-4183.
- Sima, C., C. Grigoriu, and S. Antohe. 2010. *Comparison of the Dye-sensitized Solar Cells Performances Based on Transparent Conductive ITO and FTO.* Thin Solid Films.519:595-597.
- Tamilselvan, V., D. Yuvaraj, R. R. Kumar, and K. N. Rao. 2012. *Growth of Rutile TiO₂ Nanorods on TiO₂ Seed Layer Deposited by Electron Beam Evaporation.* Applied Surface Science.258:4283-4287.
- Zhang, D., T. Yoshida, T. Oekermann, K. Furuta, and H. Minoura. 2006. *Room-temperature Synthesis of Porous Nanoparticulate TiO₂ Films for Flexible Dye-sensitized Solar Cells.* Advanced Functional Materials.16:1228-1234.
- Zhu, M., X. Li, W. Liu, and Y. Cui. 2014. *An Investigation on The Photoelectrochemical Properties of Dye-sensitized Solar Cells Based on Graphene- TiO₂ Composite Photoanodes.* Journal of Power Sources.262:349-355.